

Steel wire for mechanical springs —

Part 3: Stainless spring steel wire

The European Standard EN 10270-3:2001 has the status of a
British Standard

ICS 77.140.25

National foreword

This British Standard is the official English language version of EN 10270-3:2001. It supersedes BS 2056:1991 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee ISE/26, Steel wire, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the BSI Standards Catalogue under the section entitled “International Standards Correspondence Index”, or by using the “Find” facility of the BSI Standards Electronic Catalogue.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

This British Standard, having been prepared under the direction of the Engineering Sector Committee, was published under the authority of the Standards Committee and comes into effect on 15 May 2001

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 22, an inside back cover and a back cover.

The BSI copyright date displayed in this document indicates when the document was last issued.

Amendments issued since publication

Amd. No.	Date	Comments

English version

Steel wire for mechanical springs — Part 3: Stainless spring steel wire

Fils en acier pour ressorts mécaniques — Partie 3: Fils en acier inoxydable

Stahldraht für Federn — Teil 3: Nichtrostender Federstahldraht

This European Standard was approved by CEN on 19 February 2001.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Contents

Foreword	3
1 Scope	4
2 Normative references	4
3 Designation	5
4 Information to be supplied by the purchaser	5
5 Requirements	5
5.1 Manufacturing process	5
5.2 Form of delivery	6
5.3 Surface finish	6
5.4 Chemical composition	6
5.5 Mechanical properties	8
5.6 Technological properties	8
5.7 Supply conditions of wire on coils/reels and spools	9
5.8 Surface quality	10
5.9 Inner soundness	10
5.10 Dimensions and dimensional tolerances	11
6 Testing and inspection	12
6.1 Inspection and inspection documents	12
6.2 Extent of testing for specific testing	12
6.3 Sampling	14
6.4 Test methods	14
6.5 Retests	15
7 Marking and packaging	15
Annex A (informative) Additional information	16
Annex B (informative) Cross reference of steel grade designations	21
Bibliography	22

Foreword

This European Standard has been prepared by Technical Committee ECISS/TC 30, Steel wires, the Secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2001, and conflicting national standards shall be withdrawn at the latest by October 2001.

This European Standard for steel wire for mechanical springs is composed of the following parts:

Part 1: Patented cold drawn unalloyed spring steel wire

Part 2: Oil hardened and tempered spring steel wire

Part 3: Stainless spring steel wire

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

1 Scope

1.1 This Part of EN 10270 applies to the grades of stainless steels listed in Table 1, which are usually used in the cold drawn condition in the form of wire of circular cross-section up to 10,00 mm in diameter, for the production of springs and spring parts that are exposed to corrosive effects and sometimes to slightly increased temperatures (see A.1).

1.2 In addition to the steels listed in Table 1 certain of the steel grades covered by EN 10088-3, e.g. 1.4571, 1.4539, 1.4028, are also used for springs, although to much lesser extent. In these cases the mechanical properties (tensile strength, etc.) should be agreed between purchaser and supplier. Similarly, diameters between 10,00 mm and 15,00 mm may be ordered against this standard; in this case the parties should agree upon the required mechanical characteristics.

1.3 In addition to this part of EN 10270 the general technical delivery requirements of EN 10021 are applicable.

2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies (including amendments).

EN 10002-1, *Metallic materials — Tensile test — Part 1: Method of test (at ambient temperature)*

EN 10021, *General technical delivery requirements for steel and iron products*

EN 10027-1, *Designation systems for steel — Part 1: Steel names, principal symbols*

EN 10027-2, *Designation systems for steel — Part 2: Steel numbers*

EN 10088-3, *Stainless steels — Part 3: Technical delivery conditions for semi-finished products, bars, rods and sections for general purposes.*

EN 10204, *Metallic products — Types of inspection documents*

EN 10218-1, *Steel wire and wire products — General — Part 1: Test methods*

EN 10218-2, *Steel wire and wire products — General — Part 2: Dimensions and tolerances*

CR 10261, *Iron and steel — Review of available methods of chemical analysis*

EN ISO 377, *Steel and steel products — Location and preparation of samples and test pieces for Mechanical testing*

ISO 14284, *Steel and iron — Sampling and preparation of samples for the determination of chemical composition*

3 Designation

For products supplied according to this standard the designation shall state in the following order:

- the term spring wire or straightened and cut lengths;
- the number of this European standard: EN 10270-3;
- the steel grade, and where applicable the tensile strength level;
- the nominal wire diameter;
- the coating, if any.

EXAMPLE: Standard designation of a stainless steel spring wire according to this standard - grade 1.4310 - normal strength level and nominal diameter 2,50 mm, nickel coated:

Spring wire EN 10270-3 - 1.4310 - NS - 2,50 Ni coated

4 Information to be supplied by the purchaser

The purchaser shall clearly state in his enquiry or order the product and following information:

- a) the desired quantity;
- b) the number of this European Standard: EN 10270-3;
- c) the steel grade and, for grade 1.4310, also the tensile strength level;
- d) the nominal wire diameter;
- e) the surface finish (see 5.3) ;
- f) the form of delivery (see 5.2);
- g) the type of inspection document (see 7.1) to be supplied;
- h) any particular agreement made.

EXAMPLE: 2 t stainless spring steel wire EN 10270-3 - 1.4310 - NS - 2,50 nickel coated in coils inspection document EN 10204 - 3.1.B

5 Requirements

5.1 Manufacturing process

Unless otherwise agreed in the order, the manufacturing process used in the making of the stainless steel wire is left to the discretion of the manufacturer. The starting condition (+AT: solution annealed) of the wire (rod) is specified in EN 10088-3.

5.2 Form of delivery

The wire shall be supplied in coils, on spools, on spoolless cores or carriers. Several coils may be assembled on a carrier. Unless otherwise specified the form of delivery shall be at the manufacturer's discretion. He shall however inform the purchaser about the form of delivery.

The delivery requirements are specified in 5.7.

Wire in straight lengths is normally supplied in bundles.

5.3 Surface finish

The wire may be coated or not. The specific coating and finish for stainless steel spring wire shall be agreed upon at the time of enquiry and order, e.g. uncoated, polished finish, nickel coated.

5.4 Chemical composition

5.4.1 The requirements for the chemical composition given in Table 1 apply to the heat analysis.

5.4.2 The permissible deviation of the product analysis from the values specified in Table 1 shall be in accordance with the provision in EN 10088-3. For a single heat the deviation of an element in the product analysis may be only below the minimum or only above the maximum value of the range specified for the heat analysis, but not both at the same time.

Table 1 — Chemical composition — Heat analysis (% by mass) ^a

Steel grade		C	Si max.	Mn max.	P max.	S max.	Cr	Mo	Ni	Others
Name ^b	Number ^b									
X10CrNi18-8	1.4310	0,05 to 0,15	2,00	2,00	0,045	0,015	16,00 to 19,00	≤ 0,80	6,00 to 9,50	N:≤ 0,11
X5CrNiMo17-12-2	1.4401 ^c	≤ 0,07	1,00	2,00	0,045	0,015	16,50 to 18,50	2,00 to 2,50 ^c	10,00 to 13,00	N:≤ 0,11
X7CrNiAl17-7	1.4568	≤ 0,09	0,70	1,00	0,040	0,015	16,00 to 18,00		6,50 to 7,80 ^d	Al: 0,70 to 1,50

^a Alternative compositions may be used by agreement.

^b Names and numbers are derived in accordance with EN 10027 — Part 1 and Part 2 respectively.

^c Steel 1.4436 may be used to provide increased corrosion resistance compared with 1.4401, with the specification of this part of EN 10270 applicable for steel 1.4401.

^d For better cold formability the upper limit may be increased to 8,30 %.

Table 2 — Tensile strength in the drawn condition

Steel grade	Tensile strength (MPa) ^{a b c d e f}			
	1.4310		1.4401	1.4568
Nominal diameter (mm) ^g	Normal tensile strength (NS), min.	High tensile strength (HS), min.	min.	min.
$d \leq 0,20$	2 200	2 350	1 725	1 975
$0,20 < d \leq 0,30$	2 150	2 300	1 700	1 950
$0,30 < d \leq 0,40$	2 100	2 250	1 675	1 925
$0,40 < d \leq 0,50$	2 050	2 200	1 650	1 900
$0,50 < d \leq 0,65$	2 000	2 150	1 625	1 850
$0,65 < d \leq 0,80$	1 950	2 100	1 600	1 825
$0,80 < d \leq 1,00$	1 900	2 050	1 575	1 800
$1,00 < d \leq 1,25$	1 850	2 000	1 550	1 750
$1,25 < d \leq 1,50$	1 800	1 950	1 500	1 700
$1,50 < d \leq 1,75$	1 750	1 900	1 450	1 650
$1,75 < d \leq 2,00$	1 700	1 850	1 400	1 600
$2,00 < d \leq 2,50$	1 650	1 750	1 350	1 550
$2,50 < d \leq 3,00$	1 600	1 700	1 300	1 500
$3,00 < d \leq 3,50$	1 550	1 650	1 250	1 450
$3,50 < d \leq 4,25$	1 500	1 600	1 225	1 400
$4,25 < d \leq 5,00$	1 450	1 550	1 200	1 350
$5,00 < d \leq 6,00$	1 400	1 500	1 150	1 300
$6,00 < d \leq 7,00$	1 350	1 450	1 125	1 250
$7,00 < d \leq 8,50$	1 300	1 400	1 075	1 250
$8,50 < d \leq 10,00$	1 250	1 350	1 050	1 250

^a Tensile strength calculated on actual diameter.

^b The maximum tensile strength shall be the min. value plus 15 % of the minimum value. The range of tensile strength values within a production batch of the same heat shall be maximum 9 % of the minimum values in this table.

^c After straightening, the tensile strength may be reduced by up to 10 %.

^d When better formability is required, lower tensile strength values may be agreed upon.

^e The wire is supplied in the cold drawn condition. The tensile strength in the finished spring may be substantially influenced by a heat treatment; particularly precipitation hardening of grade 1.4568 results in substantially higher tensile strength (see A.5.2 and Table A.3).

^f 1 MPa = 1 N/mm²

^g Larger diameters may be specified in which case the parties shall agree the tensile strength at the time of enquiry and order.

5.5 Mechanical properties

5.5.1 For the tensile strength in the as drawn condition the data of Table 2 shall apply.

NOTE 1 Grade 1.4310 can be delivered in normal tensile strength (NS) or high tensile strength (HS).

NOTE 2 For steel 1.4568 the characteristics of the springs are not only determined by the characteristics of the drawn wire but also by the heat-treatment of the spring (see A.2). Therefore the steel should be of such quality so that by the heat treatment after drawing the mechanical properties are met.

5.5.2 In addition to the requirements of Table 2 the maximum tensile strength range within one unit package (individual coil, spool or reel,...) shall satisfy Table 3.

For straightened and cut lengths the values of Table 3 apply for the individual bundles.

**Table 3 — Tensile strength range within an individual unit package
(coil/spool/bundle)**

Wire diameter d (mm)	Max. range (MPa)
$d \leq 1,50$	100
$1,50 < d \leq 10,00$	70

5.6 Technological properties

5.6.1 Coiling test

For evaluation of uniformity of coiling and surface condition the coiling test may be applied to wire with a diameter of 0,50 mm to 1,50 mm. The spring coiled in accordance with 6.4.3 shall show a defect free surface condition without splits or fracture; the coil shall have uniform pitch of the turns and a fair dimensional regularity of its diameter.

NOTE Although the usefulness of the coiling test is not generally recognized, it has been retained since it offers the possibility of revealing internal stresses. If doubtful test results are obtained the wire concerned should not be rejected immediately but efforts should be made by the parties concerned to elucidate the cause.

5.6.2 Wrapping test

The wrapping test may be applied to wire with a diameter of 0,30 mm to 3,00 mm. The wire shall not show any sign of cracks or surface imperfections when closely wrapped eight turns around a mandrel of a diameter equal to the wire size (see also 6.4.4).

5.6.3 Bend test

Where requested, the bend test may be applied for wire with a diameter over 3,00 mm. The wire shall withstand the test without any sign of failure.

NOTE In some applications the material is severely deformed by bending. Such is the case for extension springs with tight hooks, springs with bends on legs, spring wire forms, etc. In such cases the bend test provides for a wire test very close to actual use.

5.7 Supply conditions of wire on coils/reels and spools

5.7.1 General

The wire of each coil shall consist of one single length of wire originating from only one heat. It shall be wound so that there are no kinks.

Where wire is delivered on spools, spoolless cores or carriers up to 10 % of those may consist of a maximum of two wire lengths. The joints shall be properly made, suitably marked and labelled.

5.7.2 Coil size

The internal diameter of unit packages (coil/reels or spools) shall reach at least the values given in Table 4, unless otherwise agreed.

Table 4 — Wire diameter and associated minimum coil internal diameter

Wire diameter (d) (mm)	Minimum internal diameter (mm)
$0,18 \leq d \leq 0,28$	100
$0,28 < d \leq 0,50$	150
$0,50 < d \leq 0,70$	180
$0,70 < d \leq 1,60$	250
$1,60 < d \leq 4,50$	400
$4,50 < d$	500

5.7.3 Circular wire cast

The wire shall be uniformly cast and take a circular cast. Unless otherwise specified the wire diameter of the wire supplied in coils/reels may expand when the binding wires are removed, but should usually not retract to less than the unit internal diameter, other than by agreement between supplier and purchaser. The expansion shall be approximately even within a single unit package and within all the units in a production batch.

5.7.4 Helix cast of wire

The wire shall be dead cast, free from helix cast. The requirement shall be considered fulfilled in the case of wire below 5,00 mm if the following condition is satisfied.

An individual wap taken from a unit package and freely hung on a hook may show an axial displacement, f , at the ends of the wap (see Figure 1); the displacement f shall not exceed a value given by the following equation :

$$f \leq \frac{0,2D}{\sqrt[4]{d}}$$

where:

- f : the axial displacement in mm
 D : the diameter of the free wap in mm
 d : the diameter of the wire in mm

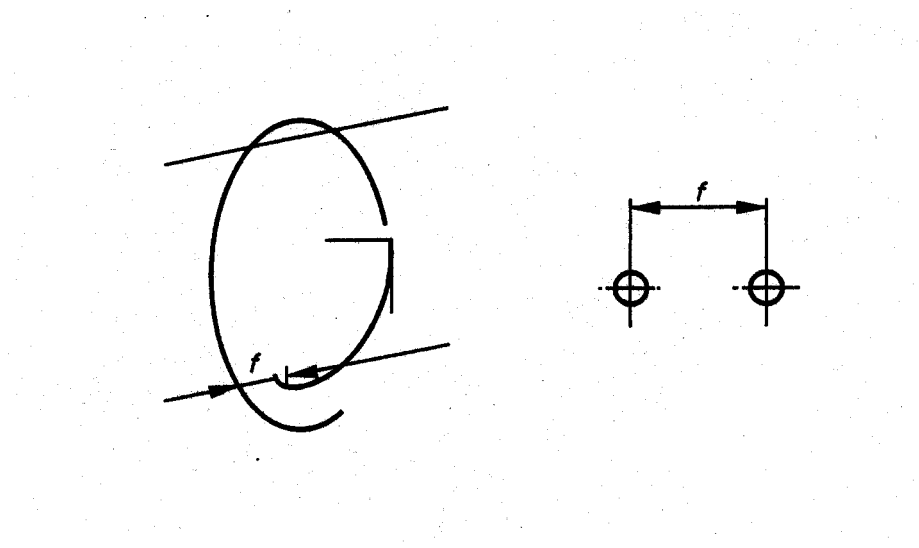


Figure 1 — Helix cast of wire

5.8 Surface quality

5.8.1 The surface of the wire shall be as far as practically possible free from grooves, pits and other surface defects, which could impair proper use of the wire. One method to reveal surface discontinuities is the reverse torsion test (see 6.4.6).

5.8.2 In cases where the wire is intended for high-duty springs, the purchaser and the supplier may agree at the time of order about special surface requirements and tests.

5.9 Inner soundness

The wire shall be sound and free from any inhomogeneity or defect that significantly limits its use.

Tests appropriate for an assessment of the inner soundness of the wire, such as the wrapping test, may be agreed upon at the time of ordering.

5.10 Dimensions and dimensional tolerances

5.10.1 Tolerances on diameter

The tolerances on diameter are given in Table 5:

Table 5 — Diameter tolerances

Nominal diameter (<i>d</i>) (mm)	Diameter tolerance (mm)		
	Spools or coils	Cut lengths	
		Lower tolerance	Upper tolerance
$d < 0,21$	$\pm 0,005$	$-0,005$	$+0,009$
$0,21 \leq d < 0,26$	$\pm 0,005$	$-0,005$	$+0,009$
$0,26 \leq d < 0,41$	$\pm 0,008$	$-0,008$	$+0,018$
$0,41 \leq d < 0,65$	$\pm 0,008$	$-0,008$	$+0,018$
$0,65 \leq d < 0,81$	$\pm 0,010$	$-0,010$	$+0,025$
$0,81 \leq d < 1,01$	$\pm 0,010$	$-0,010$	$+0,025$
$1,01 \leq d < 1,61$	$\pm 0,015$	$-0,015$	$+0,040$
$1,61 \leq d < 2,26$	$\pm 0,015$	$-0,015$	$+0,050$
$2,26 \leq d < 3,20$	$\pm 0,020$	$-0,020$	$+0,070$
$3,20 \leq d < 4,01$	$\pm 0,020$	$-0,020$	$+0,080$
$4,01 \leq d < 4,51$	$\pm 0,025$	$-0,025$	$+0,100$
$4,51 \leq d < 6,01$	$\pm 0,025$	$-0,025$	$+0,120$
$6,01 \leq d < 6,26$	$\pm 0,025$	$-0,025$	$+0,120$
$6,26 \leq d < 7,01$	$\pm 0,030$	$-0,030$	$+0,135$
$7,01 \leq d < 9,01$	$\pm 0,030$	$-0,030$	$+0,160$
$9,01 \leq d < 10,00$	$\pm 0,035$	$-0,035$	$+0,185$

5.10.2 Out of roundness

The out of roundness, i.e. the difference between the maximum and minimum diameter of the wire in the same cross section of the wire, shall not be more than 50 % of the total permissible deviation for wire in coils, specified in Table 5. For special applications tighter tolerances may be agreed at the time of enquiry and order.

5.10.3 Tolerance on the length of straightened and cut lengths

The requirements for length tolerance and straightness are as in EN 10218-2. The tolerance on the length shall only be in plus keeping the same tolerance range (see Table 6).

Table 6 — Tolerance on the length of straightened and cut wire

Nominal length (<i>L</i>) (mm)	Length tolerance		
	Class 1	Class 2	Class 3
$L \leq 300$	+ 1,00 mm 0 mm	1 % 0 %	2 % 0 %
$300 < L \leq 1\,000$	+ 2,00 mm 0 mm		
$1\,000 < L$	+ 0,2 % 0 %		

6 Testing and inspection

6.1 Inspection and inspection documents

Products conforming with this standard shall be delivered with specific testing (see EN 10021) and the relevant inspection document (see EN 10204) agreed at the time of enquiry and order.

The inspection document shall include the following information:

- the document number;
- the date of issue;
- the customer's order number and name;
- the designation according to clause 3;
- the tests, their results and where appropriate in a statistical way;
- the identification by production lot number and heat number;
- the heat analysis;
- results of optional tests agreed.

6.2 Extent of testing for specific testing

The extent of testing shall be in accordance with Table 8.

Table 8 — Extent of testing and sampling for specific testing and summary of the information on test procedure and requirements

	1	2	3	4	5	6	7	8	9	10	
	Test method	Applies to wire grades	^a	Test unit	Number of products per test unit	Number of samples per product	Number of test pieces per sample	Sampling	Test procedure in accordance with sub-clause	Requirements ^b See sub-clause	
1	Product analysis	All	o ^b	Quantity supplied per heat	1	1	1	As per ISO 14284	6.4.1	5.4 ^b	
2	Tensile test	All	m	Quantity supplied per production batch ^d	10 % ^c	1	1	Test pieces taken from the ends of the coils	6.4.2	5.5 ^d	
3	Coiling test	0,5 mm ≤ <i>d</i> ≤ 1,5 mm	o		The scope of testing shall be agreed on ordering				6.4.3	5.6.1	
4	Wrapping test	0,3 mm ≤ <i>d</i> ≤ 3 mm	o						6.4.4	5.6.2	
5	Bend test	<i>d</i> > 3 mm	o						6.4.5	5.6.3	
6	Testing for freedom from twists	All	m	10 % ^c	1	1	To be agreed at the order		6.4.7	5.7.3	
7	Testing for surface quality	All	o						6.4.6	5.8 ^d	
8	Check on dimensions	All	m	100 %	1	1			EN 10218-1	5.10	

^a m (= mandatory); the test is to be carried out in each case / o (= optional); the test is carried out only if so agreed at the time of ordering.

^b The results of the cast analysis for the elements listed in Table 1 for the grade concerned shall be notified to the customer in all cases.

^c 10 % of the wire units in the production batch, at least 2 but no more than 10 coils/reels or spools.

^d A production batch is defined as a quantity of production originating from the same cast, which has been subjected to the same conditions of heat treatment, and with the same reduction in cross-section and with the same surface finish.

^a m (= mandatory): the test is to be carried out in each case / o (= optional): the test is carried out only if so agreed at the time of ordering.

^b The results of the cast analysis for the elements listed in Table 1 for the grade concerned shall be notified to the customer in all cases.

^c 10 % of the wire units in the production batch, at least 2 but no more than 10 coils/reels or spools.

^d A production batch is defined as a quantity of production originating from the same cast, which has been subjected to the same conditions of heat treatment, and with the same reduction in cross-section and with the same surface finish.

6.3 Sampling

Sampling and testing preparation shall be in accordance with EN ISO 377 and ISO 14284.

Samples shall be taken at the end of the coils, reels or spools or at random for wire in the form of straightened and cut lengths. Table 8/column 8 gives further details.

6.4 Test methods

6.4.1 Chemical composition

Unless otherwise agreed at the time of ordering the choice of a suitable physical or chemical method of analysis for the determination of product analysis shall be at the discretion of the supplier.

In cases of dispute the analysis shall be carried out by a laboratory approved by the two parties. The method of analysis to be applied shall be agreed upon, where possible in accordance with CR 10261.

6.4.2 Tensile test

The tensile test shall be carried out according to EN 10002-1, on samples with the full cross-section of the wire. For the calculation of the tensile strength the actual cross-section based on the actual wire diameter is applied.

6.4.3 Coiling test

The coiling test shall be carried out in the following manner: A test piece, approximately 500 mm in length, shall be closely wound, under slight but reasonably uniform tension on a mandrel three to three and a half times the nominal diameter. The mandrel diameter shall however be at least 1,00 mm. The close coil shall be stretched so that after releasing the stress it sets to approx. three times its original length.

The surface condition of the wire and the regularity of the spring pitch and individual windings shall be inspected with the test piece in this condition.

6.4.4 Wrapping test

The wrapping test for ductility shall be carried out according to EN 10218-1. The wire shall be wrapped 8 turns around a mandrel with a diameter equal to the wire diameter.

6.4.5 Bend test

For the bend test a wire sample of sufficient length shall be bent in U form around a mandrel with a diameter equal to twice the wire diameter for sizes above 3,00 mm to 6,50 mm and equal to three times the wire diameter for sizes above 6,50 mm. For practical reasons the wire shall be deemed to have met the requirements of this standard if it withstands bending around a mandrel smaller than the one specified.

In carrying out the test the wire shall be free to move longitudinally in the forming device.

6.4.6 Reverse torsion test

The torsion test shall be carried out according to EN 10218-1 with the specific requirement that the wire is twisted first 2 complete turns in one direction and then 2 turns back in the other direction without revealing surface cracks visible to the naked eye.

The distance between the clamps shall be 100 d with a maximum of 300 mm.

6.4.7 The wire cast

The circular and helix cast as defined in EN 10218-1 shall be tested on a sufficiently long piece of wire so as to form a full free wap (single convolution of wire) ensuring that it is not bent or mechanically damaged.

6.5 Retests

Retests shall be carried out according to EN 10021.

7 Marking and packaging

Each unit shall be properly marked and identified so as to permit identification, traceability and reference to the inspection documents. The labels shall withstand normal handling and show the information according to Table 7. Other information shall be subject of an agreement between the parties.

Wire shipments shall be suitably protected against mechanical damage and/or contamination during transport.

Table 7 — information on the labels ^a

Designation	+
Manufacturer	+
Nominal diameter	+
Steel grade	+
Tensile strength grade	+ ^b
Surface finish	(+)
Cast number	(+)
Identification number	+ ^b
Coating	+ ^b
^a The symbols in the table mean: + : The information shall be mentioned on the labels. (+): The information shall be mentioned on the labels if so agreed. ^b Only where applicable.	

Annex A (informative)

Additional information

A.1 Indications for classification of steel grades

Depending on stress, the maximum temperature of use of the steel grade number 1.4310 is up to 250 °C.

If greatest resistance to corrosion is required for one of the steels covered by this part of EN 10270, the austenitic grade number 1.4401 may be used, also depending on stress for a maximum temperature of use up to 250 °C.

The maximum for the precipitation-hardenable austenitic-martensitic steel grade number 1.4568 is up to 300 °C depending on stress. This steel has a high fatigue strength and an increased strength at elevated temperatures, but a reduced resistance to corrosion.

The various grades of steel have slightly different values for the modulus of elasticity, determined on longitudinal test pieces, and for the shear modulus (see Table A.1). It should be taken into account that with increasing temperature the values of the modulus of elasticity and shear modulus decrease.

Table A.1 — Reference data for the modulus of elasticity and shear modulus (mean values) ^{a b c}

Steel grade		Modulus of elasticity ^a		Shear modulus ^b	
Name	Number	Delivery ^d Condition GPa	Condition ^d HT ^e GPa	Delivery ^d condition GPa	Condition ^d HT ^e GPa
X10CrNi18-8	1.4310	180	185	70	73
X5CrNiMo17-12-2	1.4401	175	180	68	71
X7CrNiAl17-7	1.4568	190	200	73	78

^a The reference data for the modulus of elasticity (E) are calculated from the shear modulus (G) by means of the formula $G = E/2 (1+\nu)$ where ν (Poisson's constant) is set to 0,3. The data are applicable for a mean tensile strength of 1 800 MPa. For a mean tensile strength of 1 300 MPa, the values are 6 GPa lower. Intermediate values may be interpolated

^b The reference data for the shear modulus (G) are applicable to wires with a diameter $\leq 2,8$ mm for measurements by means of a torsion pendulum, for a mean tensile strength of 1 800 MPa. For a mean tensile strength of 1 300 MPa, the values are 2 GPa lower. Intermediate values may be interpolated. Values ascertained by means of an Elastomat are not always comparable with values ascertained by means of a torsion pendulum.

^c For the finished spring, lower values may be ascertained. Therefore, standards for calculation of springs may specify values different from those given here on the basis of measurement of wire.

^d 1 MPa = 1 N/mm², 1 GPa = 1 kN/mm²

^e HT treated: See A.5 and Table A.2.

A.2 Alteration of tensile strength by heat treatment

The heat treatment of stress-relieving (tempering) or in the case of steel grade 1.4568 precipitation hardening will increase tensile strength and yield strength values as compared with the cold drawn condition (+C). Heat treatments of this kind will also reduce the internal stresses in the wire produced by drawing and spring forming.

The increase in the tensile strength of grade 1.4568 caused by the precipitation hardening is greater than that caused by the stress relieving of other grades in this standard. Where the wire has been straightened before the heat treatment, the loss in tensile strength caused by the straightening can be almost compensated for.

Consequently, final stress-relieving or precipitation hardening of the finished springs is a basic recommendation. Reference data for the heat treatment are given in A.5.2 and Table A.2.

Data on the increase in tensile strength by this heat treatment are given in Figure A.1 and Table A.3 for 1.4568+P.

The heat treatment can cause out of straightness and also some discolouration.

A.3 Physical properties

Reference data for the modulus of elasticity and shear modulus are given in Table A.1. Further physical properties (e.g. density, ...) are given in EN 10088-1.

A.4 Magnetic properties

It should be noted that, depending upon chemical composition and degree of cold deformation condition, these steels show some degree of magnetic permeability. (See EN 10088-1).

A.5 Guidelines for processing and heat treatment

A.5.1 Spring forming

Forming is carried out by cold deformation. Therefore, account has to be taken of the fact that the deformability of cold-worked, cold-drawn wire is limited. Depending on the forming requirements, a lower tensile strength may be agreed upon when ordering (see footnote d to Table 2).

Table A.2 — Reference data for heat treatment of springs made of wire ^{a b c} - See also A.5.2

Steel grade		Temperature (°C)	Duration	Means of cooling
Name	Number			
X10CrNi18-8	1.4310	250-425	30 min to 4 h	air
X5CrNiMo17-12-2	1.4401	250-425	30 min to 4 h	air
X7CrNiAl17-7	1.4568	450-480	30 min to 1 h	air

^a See classification of the tensile strength data in Table 2 and Figure A.1.

^b The optimum heat treatment conditions may be very different. The spring manufacturer shall choose those conditions answering the purpose, see also A.5.2.1.

^c The heat treatment data refer to compression springs, torsion and tension(springs without initial tension. Generally, tension springs and torsion springs with initial tension are not to be treated at the same high temperature as above mentioned springs. If moderate loss of initial tension can be accepted, heat treatment temperatures of max. 200 °C for grades number 1.4310, 1.4401 and 300 °C for grade number 1.4568 are recommended.

A.5.2 Heat treatment

A.5.2.1 Table A.2 contains reference data on heat treatment to be carried out on finished springs in order to achieve suitable strength and elastic properties. In special cases, modified heat treatments, to be determined by practical trials, will be necessary to meet specific requirements.

A.5.2.2 The springs should be thoroughly cleaned before heat treatment. If the colours produced by heat treatment are not permissible for visual or corrosion-resistance reasons, the heat treatment may be carried out in a protective atmosphere, or a suitable cleaning process may be used which does not impair the spring properties.

**Table A.3 — Expected minimum tensile strength for
precipitation hardened 1.4568**

Nominal diameter (mm)	Tensile strength (MPa)
$d \leq 0,20$	2 275
$0,20 < d \leq 0,30$	2 250
$0,30 < d \leq 0,40$	2 225
$0,40 < d \leq 0,50$	2 200
$0,50 < d \leq 0,65$	2 150
$0,65 < d \leq 0,80$	2 125
$0,80 < d \leq 1,00$	2 100
$1,00 < d \leq 1,25$	2 050
$1,25 < d \leq 1,50$	2 000
$1,50 < d \leq 1,75$	1 950
$1,75 < d \leq 2,00$	1 900
$2,00 < d \leq 2,50$	1 850
$2,50 < d \leq 3,00$	1 800
$3,00 < d \leq 3,50$	1 750
$3,50 < d \leq 4,25$	1 700
$4,25 < d \leq 5,00$	1 650
$5,00 < d \leq 6,00$	1 550
$6,00 < d \leq 7,00$	1 500
$7,00 < d \leq 8,50$	1 500
$8,50 < d \leq 10,00$	1 500

Increase in tensile strength, MPa

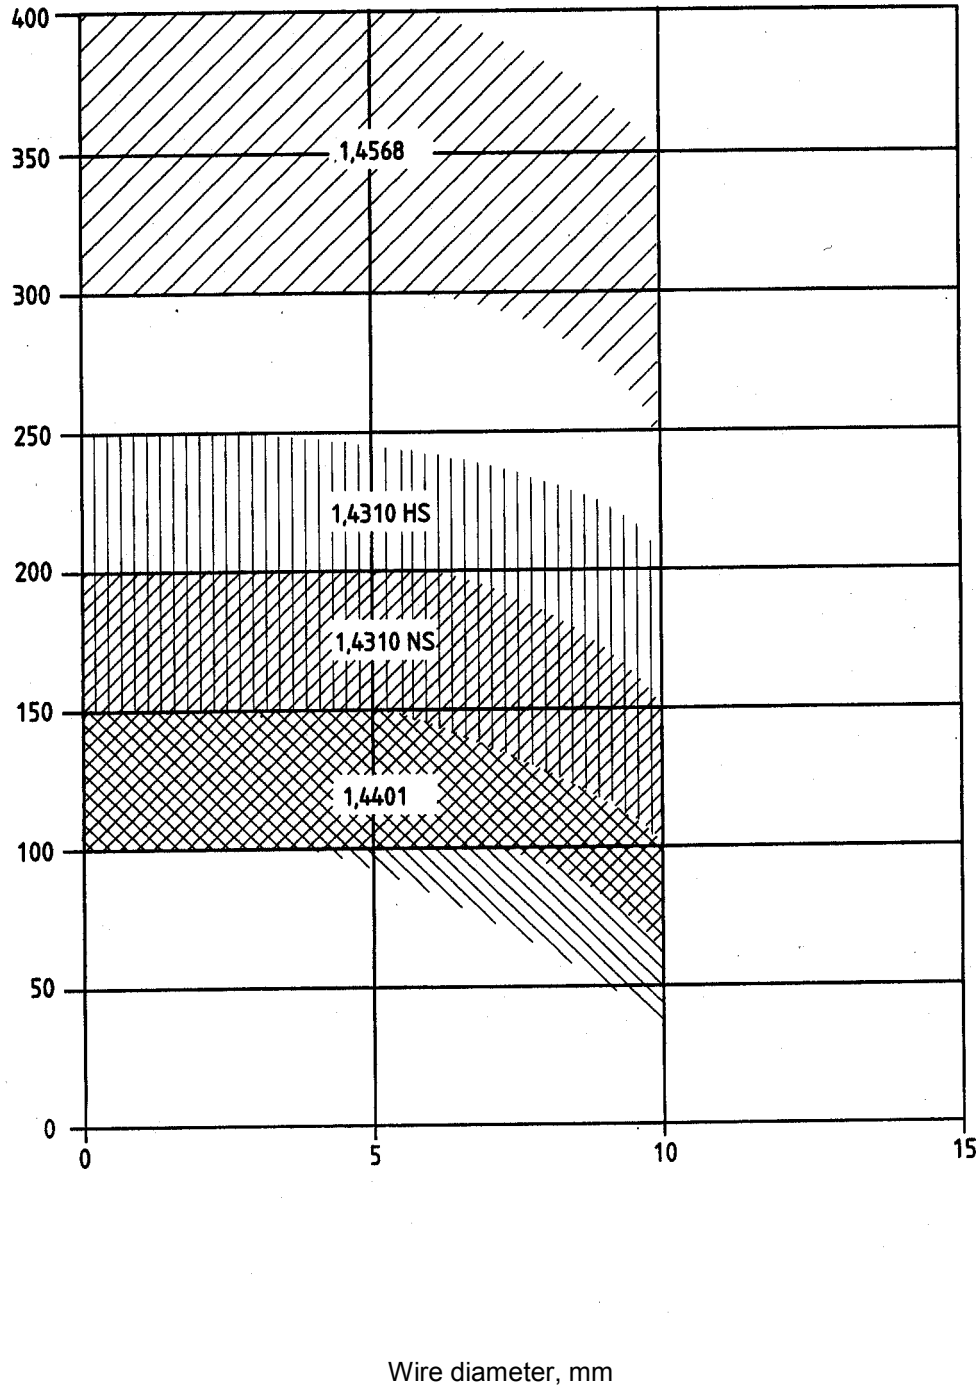


Figure A.1 — Reference data for the increase in tensile strength of cold drawn wire by heat treatment (see Table A.2)

Annex B (informative)
Cross reference of steel grade designations

Table B.1 — Cross reference of steel grade designations

Designation in EN 10270-3		Corresponding former designation				ISO-designation
According to EN 10027-1	According to EN 10027-2	DIN 17224: 1982	AFNOR	BS 2056: 1991	MMS 900	ISO 6931-1: 1994
X10CrNi18-8	1.4310	X 12 CrNi 17-7	1.4310	Z 12 CN 18-09	302S26	SS-steel 2331 Number 1 X 9 CrNi 18-8
X5CrNiMo17-12-2	1.4401	X 5 CrNiMo 18-10	1.4401	Z 7 CND 17-11-02	316S42	SS-steel 2347 Number 2 X 5 CrNiMo 17-12-2
X7CrNiAl17-7	1.4568	X 7 CrNiAl 17-7	1.4568	Z 9 CNA 17-07	301S81	SS-steel 2388 Number 3 X 7 CrNiAl 17-7

Bibliography

EN 10088-1, *Stainless steels — Part 1: List of stainless steels*

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.
Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001. Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.
Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.
Tel: 020 8996 7002. Fax: 020 8996 7001. Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager.
Tel: 020 8996 7070.