

Hot rolled sheet piling of non alloy steels —

Part 2: Tolerances on shape and dimensions

The European Standard EN 10248-2:1995 has the status of a
British Standard

ICS 77.140.70

Committees responsible for this British Standard

The preparation of this British Standard was entrusted to Technical Committee ISE/12, Structural steels, upon which the following bodies were represented:

- BEAMA Ltd.
- British Constructional Steelwork Association Ltd.
- British Iron and Steel Producers' Association
- British Railways Board
- Department of Transport
- Institution of Structural Engineers
- Lloyd's Register of Shipping
- National Association of Steel Stockholders
- Railway Industry Association
- Society of Motor Manufacturers and Traders Limited
- Steel Construction Institute
- Welding Institute

This British Standard, having been prepared under the direction of the Engineering Sector Board, was published under the authority of the Standards Board and comes into effect on 15 March 1996

© BSI 12-1999

The following BSI references relate to the work on this standard:
Committee reference ISE/12
Draft for comment 93/309093 DC

ISBN 0 580 24937 9

Amendments issued since publication

Amd. No.	Date	Comments

Contents

	Page
Committees responsible	Inside front cover
National foreword	ii
Foreword	2
Text of EN 10248-2	3

National foreword

This British Standard has been prepared by Technical Committee ISE/12 and is the English language version of EN 10248-2:1995 *Hot rolled sheet piling of non alloy steels — Part 2: Tolerances on shape and dimensions*, published by the European Committee for Standardization (CEN).

Cross-references

Publication referred to	Corresponding British Standard
EN 10248-1	BS EN 12048-1 <i>Hot rolled sheet Piling of non alloy steels</i> Part 1:1996 <i>Technical delivery conditions</i>

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, the EN title page, pages 2 to 9 and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.

ICS 77.140.70

Descriptors: Iron and steel products, hot rolled products, sheet pilings, steels, unalloyed steels, dimensions, dimensional tolerances, form tolerances

English version

Hot rolled sheet piling of non alloy steels — Part 2: Tolerances on shape and dimensions

Palplanches laminées à chaud en aciers non
alliés — Partie 2: Tolérances sur forme et
dimensions

Warmegewalzte Spundbohlen aus unlegierten
Stählen — Teil 2: Grenzabmaße und
Formtoleranzen

This European Standard was approved by CEN on 1995-05-19. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart 36, B-1050 Brussels

Foreword

This European Standard was prepared by Subcommittee SC4, Sheet piling, of Technical Committee ECISS/TC10, Structural steels — Qualities, of which the secretariat is held by NNI.

EN 10248 is composed of two Parts:

- *Part 1: Technical delivery conditions;*
- *Part 2: Tolerances on shape and dimensions.*

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 1995, and conflicting national standards shall be withdrawn at the latest by December 1995.

According to the CEN/CENELEC International Regulations, the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland, United Kingdom.

Contents

	Page
Foreword	2
1 Scope	3
2 Normative references	3
3 Height of profiles	3
3.1 U-sheet piles	3
3.2 Z-sheet piles	3
3.3 H-sheet piles	4
4 Width of profiles	4
4.1 U-sheet piles	4
4.2 Z-sheet piles	4
4.3 Flat profiles	4
4.4 H-sheet piles	5
5 Wall thicknesses of profiles	5
5.1 U-sheet piles	5
5.2 Z-sheet piles	5
5.3 Flat profiles	6
5.4 H-sheet piles	6
6 Straightness of profiles (deviation from straight line)	6
7 Length of profiles	7
8 Squareness of ends for all profiles	7
9 Mass of all profiles	7
10 Interlocks of profiles	7
11 Options	8
Table 1 — Height of U-sheet piles	3
Table 2 — Height of Z-sheet piles	3
Table 3 — Height of H-sheet piles	4
Table 4 — Width of U-sheet piles	4
Table 5 — Width of Z-sheet piles	4
Table 6 — Width of flat profiles	4
Table 7 — Width of H-sheet piles	5
Table 8 — Wall thicknesses of U-sheet piles	5
Table 9 — Wall thicknesses of Z-sheet piles	5
Table 10 — Wall thickness of flat profiles	6
Table 11 — Wall thicknesses of H-sheet piles	6
Table 12 — Straightness of all profiles	6
Table 13 — Length of all profiles	7
Table 14 — Squareness of ends for all profiles	7
Table 15 — Examples of typical types of interlocks for sheet piles	8

1 Scope

This Part of this European Standard specifies the tolerances on dimensions, squareness of ends, straightness and mass of hot rolled non alloy steel sheet piles which are defined in EN 10248-1.

2 Normative references

This European Standard incorporates by dated or undated reference provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN 10248-1, *Hot rolled sheet piling of non alloy steels — Part 1: Technical delivery conditions.*

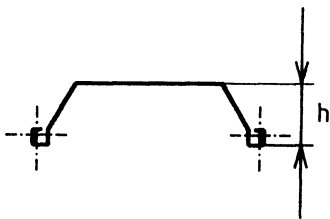
3 Height of profiles

3.1 U-sheet piles

The tolerances on the height of U-sheet piles are given in Table 1.

Table 1 — Height of U-sheet piles

Dimensions in millimetres

Designation	Figure	Nominal dimension	Tolerance
Height h		$h \leq 200$ $h > 200$	± 4 ± 5

Tolerances on the height of sections made of a pair of crimped or welded piles may be agreed at the time of the enquiry and order.

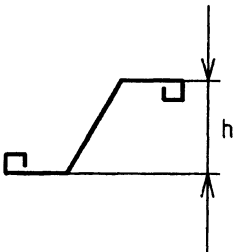
Option 1, see 11.2.

3.2 Z-sheet piles

The tolerances on the height of Z-sheet piles are given in Table 2.

Table 2 — Height of Z-sheet piles

Dimensions in millimetres


Designation	Figure	Nominal dimension	Tolerance
Height h		$h \leq 200$ $200 < h < 300$ $h \geq 300$	± 5 ± 6 ± 7

3.3 H-sheet piles

The tolerances on the height of H-sheet piles are given in Table 3.

Table 3 — Height of H-sheet piles

Dimensions in millimetres

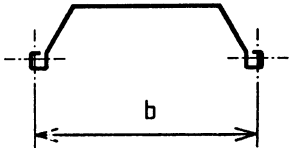
Designation	Figure	Nominal dimension	Tolerance
Height h		$h < 500$ $h \geq 500$	± 5 ± 7

4 Width of profiles¹⁾

4.1 U-sheet piles

The tolerance on the width of U-sheet piles is given in Table 4.


Table 4 — Width of U-sheet piles

Designation	Figure	Nominal dimension	Tolerance
Width b		All	$\pm 2 \% b$

4.2 Z-sheet piles

The tolerance on the width of Z-sheet piles is given in Table 5.


Table 5 — Width of Z-sheet piles

Designation	Figure	Nominal dimension	Tolerance
Width b		All	$\pm 2 \% b$

4.3 Flat profiles

The tolerance on the width of flat profiles is given in Table 6.

Table 6 — Width of flat profiles


Designation	Figure	Nominal dimension	Tolerance
Width b		All	$\pm 2 \% b$

¹⁾ For sections interlocked in double or triple piles, the tolerance from the total nominal width may be $\pm 3 \%$.

4.4 H-sheet piles

The tolerance on the width of H-sheet piles is given in Table 7.

Table 7 — Width of H-sheet piles

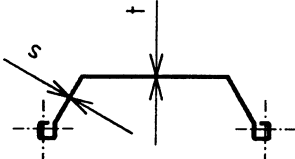
Designation	Figure	Nominal dimension	Tolerance
Width <i>b</i>		All	$\pm 2 \% b$

5 Wall thicknesses of profiles²⁾

5.1 U-sheet piles

The tolerances on wall thicknesses of U-sheet piles are given in Table 8.


Table 8 — Wall thicknesses of U-sheet piles

Dimensions in millimetres			
Designation	Figure	Nominal dimension	Tolerance
Thicknesses <i>s</i> and <i>t</i>		$t \leq 8,5$	$\pm 0,5$
		$t > 8,5$	$\pm 6 \% t$
		$s \leq 8,5$	$- 0,5^a$
		$s > 8,5$	$- 6 \% s^a$
^a Normally the positive tolerance shall be at the discretion of the manufacturer. At the time of the enquiry and order, a limitation on the positive tolerance can be agreed. In this case, the following values should be chosen: + 0,5 mm for $s \leq 8,5$ mm and + 6 % <i>s</i> for $s > 8,5$ mm (option 2, see 11.3)			

5.2 Z-sheet piles

The tolerances on wall thicknesses of Z-sheet piles are given in Table 9.

Table 9 — Wall thicknesses of Z-sheet piles


Dimensions in millimetres			
Designation	Figure	Nominal dimension	Tolerance
Thicknesses <i>s</i> and <i>t</i>		$t, s \leq 8,5$	$\pm 0,5$
		$t, s > 8,5$	$\pm 6 \% s$ and t

²⁾ Measured at centre.

5.3 Flat profiles

The tolerances on wall thickness of flat profiles are given in Table 10.


Table 10 — Wall thickness of flat profiles

Dimensions in millimetres			
Designation	Figure	Nominal dimension	Tolerance
Thickness <i>t</i>		$t \leq 8,5$ $t > 8,5$	$\pm 0,5$ $\pm 6 \% t$

5.4 H-sheet piles

The tolerances on wall thicknesses of H-sheet piles are given in Table 11.

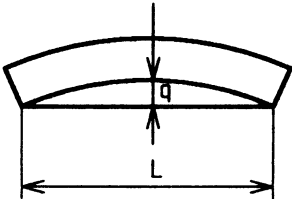
Table 11 — Wall thicknesses of H-sheet piles

Dimensions in millimetres			
Designation	Figure	Nominal dimension	Tolerance
Thicknesses <i>s</i> and <i>t</i>		$t, s \leq 12,5$ $t, s > 12,5$	$+ 2$ $- 1$ $+ 2,5$ $- 1,5$

6 Straightness of profiles (deviation from straight line)³⁾

The tolerance on straightness of profiles is given in Table 12.

Table 12 — Straightness of all profiles

Designation	Figure	Nominal dimension	Tolerance
<i>q</i>		All lengths	$\leq 0,2 \% L$

A reduced tolerance may be agreed at the time of the enquiry and order.

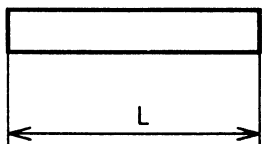
Option 3, see 11.4.

³⁾ Measuring of a pile shall be carried out on a well 1-1 aligned level surface.

7 Length of profiles

The tolerance on the length of profiles is given in Table 13.

Table 13 — Length of all profiles

Dimensions in millimetres			
Designation	Figure	Nominal dimension	Tolerance
Length L		All	± 200

A reduced tolerance may be agreed at the time of the enquiry and order.

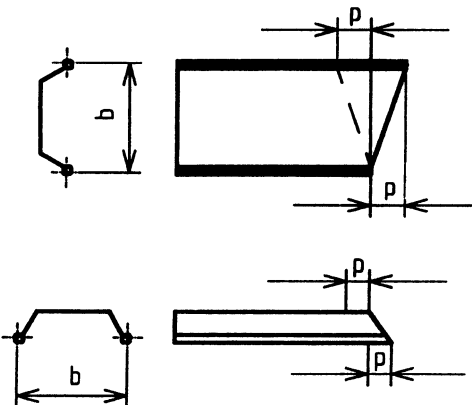
Option 4, see 11.5.

8 Squareness of ends for all profiles

The tolerance on squareness of profile ends is given in Table 14.

The total deviation between the highest and the lowest point of the cutting plane shall not exceed 2 % of b with the measurement being taken in the direction of the longitudinal axis of a single pile.

Table 14 — Squareness of ends for all profiles

Designation	Figure	Nominal dimension	Tolerance
p		All widths	$\pm 2 \% b$

9 Mass of all profiles

Compared with the calculated mass (product of ordered pile length by mass per linear metre of pile according to section tables of the producers), the actual mass shall deviate no more than $\pm 5 \%$ from the mass of the total delivery.

A reduced tolerance may be agreed at the time of the enquiry and order.

Option 5, see 11.6.

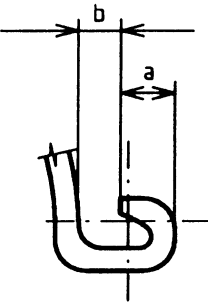
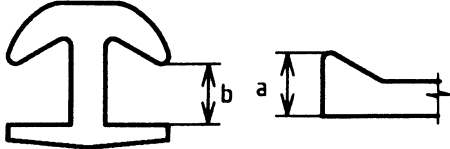
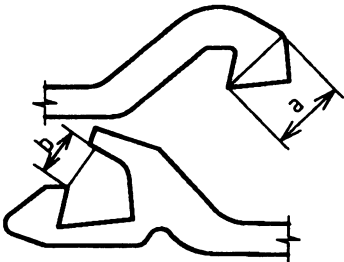
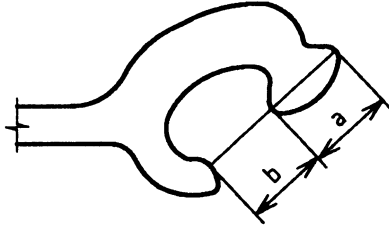
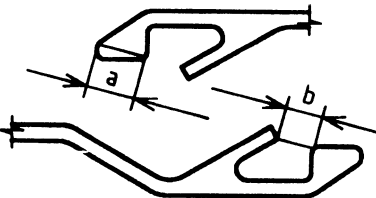
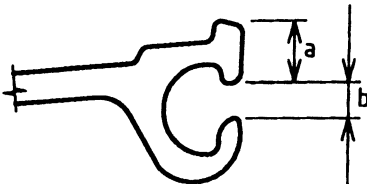
10 Interlocks of profiles

The interlocks shall have adequate free play, so that the piles can be fitted into each other and they shall engage in such a manner that the in-service forces can be transmitted. In general, the minimum interlock interference, as calculated by dimension a minus b shall comply with Table 15.

In short partial sections, the minimum values may fall short of the values by not more than 1 mm.

Table 15 — Examples of typical types of interlocks for sheet piles

Dimensions in millimetres

Type 1 a = Hook width b = Interlock opening Tolerance: $a - b \geq 4$ 	Type 4 a = Club height b = Interlock opening Tolerance: $a - b \geq 4$ 
Type 2 a = Button width b = Interlock opening Tolerance: $a - b \geq 4$ 	Type 5 a = Hook width b = Interlock opening Tolerance: $a - b \geq 2,6$ 
Type 3 a = Button width b = Interlock opening Tolerance: $a - b \geq 4$ 	Type 6 a = Hook width b = Interlock opening Tolerance: $a - b \geq 7,0$ 

11 Options

11.1 Options are available to the purchaser which shall be specified as required at the time of the enquiry and order (see 4.2 — EN 10248-1).

11.2 Option 1

If tolerances are agreed on the height of sections made of a pair of crimped or welded piles (see 3.1).

11.3 Option 2

If a plus tolerance is agreed for the thickness (s) for U-sheet piles (see 5.1).

11.4 Option 3

A reduced tolerance for the straightness of profiles (see clause 6).

11.5 Option 4

A reduced tolerance for the length of profiles (see clause 7).

11.6 Option 5

A reduced tolerance for the mass of profiles (see clause 9).

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.