

Plastics piping and ducting systems — Thermoplastics pipes — Test method for resistance to external blows by the round-the-clock method

The European Standard EN 744:1995 has the status of a
British Standard

ICS 23.040.20

Committees responsible for this British Standard

The preparation of this British Standard was entrusted to Technical Committee PRI/61, Plastics piping systems and components, upon which the following bodies were represented:

- British Gas plc
- British Plastics Federation
- British Plumbing Fittings Manufacturers' Association
- British Valve and Actuator Manufacturers' Association
- Department of the Environment (British Board of Agrément)
- Department of the Environment (Building Research Establishment)
- Department of the Environment (Property and Building Directorate)
- Department of Transport
- Electricity Association
- Federation of Civil Engineering Contractors
- Health and Safety Executive
- Institute of Building Control
- Institute of Materials
- Institution of Civil Engineers
- Institution of Gas Engineers
- Institution of Water and Environmental Management
- National Association of Plumbing, Heating and Mechanical Services Contractors
- Pipeline Industries Guild
- Plastics Land Drainage Manufacturers' Association
- Society of British Gas Industries
- Society of British Water Industries
- Water Companies Association
- Water Services Association of England and Wales

The following bodies were also represented in the drafting of the standard, through subcommittees and panels:

- ERA Technology Ltd.
- Engineering Equipment and Materials Users' Association
- RAPRA Technology Ltd.

This British Standard, having been prepared under the direction of the Sector Board for Materials and Chemicals, was published under the authority of the Standards Board and comes into effect on 15 February 1996

© BSI 07-1999

The following BSI references relate to the work on this standard:
Committee reference PRI/61
Draft for comment 92/413382 DC

ISBN 0 580 25149 7

Amendments issued since publication

Amd. No.	Date	Comments

Contents

	Page
Committees responsible	Inside front cover
National foreword	ii
Foreword	2
1 Scope	3
2 Definition	3
3 Principle	3
4 Apparatus	3
5 Test pieces	6
6 Conditioning	6
7 Procedure	6
8 Expression of results	7
9 Test report	8
Annex A (informative) Evaluation of results from isolated batches	9
Figure 1 — Typical falling weight testing machine	4
Figure 2 — Dimensions of strikers	5
Figure 3 — Number of test pieces for 10 % TIR (at 90 % confidence level)	8
Table 1 — Dimensions for the nose of the striker	3
Table 2 — Mass of strikers	3
Table 3 — Number of equidistant lines to be drawn on the test pieces	6
Table 4 — Conditioning periods	6
Table 5 — Expression of TIR at 10 % depending on the number of blows and failures	7

National foreword

This British Standard has been prepared by Technical Committee PRI/61 and is the English language version of EN 744:1995 *Plastics piping and ducting systems — Thermoplastics pipes — Test method for resistance to external blows by the round-the-clock method*, published by the European Committee for Standardization (CEN).

It is incorporated into BS 2782 *Methods of testing plastics — Part 11: Thermoplastics pipes, fittings and valves*, as Method 1108C:1995 for association with related test methods for plastics materials and plastics piping components.

This test method has been prepared for reference by other standards under preparation by CEN for specification of plastics piping systems and components. It has been implemented to enable experience of the method to be gained, and for use for other fresh applications.

It is also for use for the revision or amendment of other national standards as practicable, but it should not be presumed to apply to any existing standard or specification which contains or makes reference to a different test method until that standard/specification has been amended or revised to make reference to this method and adjust any requirements as appropriate. In particular, attention is drawn to the fact that because of e.g. differences in striker geometry, this method is not expected to give identical results to those obtained by reference to BS 2782-11:Method 1108A:1989, the use of which should be restricted to its current applications.

Pending any related amendment of EN 744:1995, attention is drawn to the requirement in clause 6 to use a bath of water and ice for conditioning at 0 °C, which may inhibit the use of equipment where the bath liquid temperature is controlled by passage through or past a heat exchanger operating at a lower temperature.

WARNING NOTE. This British Standard, which is identical with EN 744:1995, does not necessarily detail all the precautions necessary to meet the requirements of the Health and Safety at Work etc. Act 1974. Attention should be paid to any appropriate safety precautions and the method should be operated only by trained personnel.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, the EN title page, pages 2 to 10 and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.

ICS 23.040.20

Descriptors: Plastic tubes, thermoplastic resins, mechanical tests, impact test, shock resistance

English version

Plastics piping and ducting systems —
Thermoplastics pipes —
Test method for resistance to external blows by the
round-the-clock method

Systèmes de canalisations et de gaines en
plastiques — Tubes thermoplastiques —
Méthode d'essai de résistance aux chocs
externes par la méthode du cadran

Kunststoff-Rohrleitungs- und
Schutzrohrsysteme — Rohre aus
Thermoplasten — Prüfverfahren für die
Widerstandsfähigkeit gegen äußere
Schlagbeanspruchung im Umfangsverfahren

This European Standard was approved by CEN on 1995-02-06. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart 36, B-1050 Brussels

© 1995 All rights of reproduction and communication in any form and by any means reserved in all countries to CEN and its members

Ref. No. EN 744:1995 E

Foreword

This European Standard was prepared by CEN/TC 155, *Plastics piping systems and ducting systems*, of which the secretariat is held by NNI. This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 1995, and conflicting national standards shall be withdrawn at the latest by October 1995.

According to the CEN/CENELEC Internal Regulations, the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland, United Kingdom.

This standard is based on ISO/DIS 3127:1992 *Unplasticized polyvinyl chloride (PVC) pipes for the transport of fluids — Determination and specification of resistance to external blows*, prepared by the International Organization for Standardization (ISO). It is a modification of ISO/DIS 3127:1992 for reasons of applicability to other plastics materials and/or other test conditions and alignment with texts of other standards on test methods.

The modifications are:

- no pipe material is mentioned;
- test parameters, except those common to all plastics, are omitted;
- no material-dependent requirements are given;
- editorial changes have been introduced.

The material-dependent parameters and/or performance requirements are incorporated in the system standard(s) concerned.

Annex A, which is informative, gives guidance on sampling.

No existing European Standard is superseded by this standard.

This standard is one of a series of standards on test methods which support system standards for plastics piping systems and ducting systems.

1 Scope

This standard specifies a method for determining the resistance to external blows of thermoplastics pipes with circular cross sections by using the round-the-clock method.

The method is intended to be applied to isolated batches of pipe. For type testing and audit testing, 0 °C and/or – 20 °C are applicable.

NOTE Pipes made from polypropylene homopolymer (PP-H) which principally can not conform to impact requirements at 0 °C or lower temperatures are permitted to be tested at (23 ± 2) °C under the condition that PP-H pipes are intended for use for soil and waste discharge and bear an additional marking indicating that they are not to be installed below + 5 °C.

2 Definition

For the purposes of this standard, the following definition applies.

true impact rate (TIR)

the total number of failures divided by the total number of blows, in per cent, as if the whole batch had been tested

NOTE In practice, test pieces are drawn at random from the batch and the result is only an estimate of the TIR for that batch.

3 Principle

Test pieces comprising cut lengths of pipe, representative of a batch or a production run from an extruder, are subjected to blows from a falling weight dropped from a specified height on to specified positions around the circumference of the pipe. The incidence of failure is estimated as the true impact rate (TIR) of the batch, or production run, where the maximum value for TIR is 10 %.

NOTE 1 The severity of this test method can be adjusted to suit different specification needs by changing the mass of the falling weight and/or by changing the fall height. It is not technically correct to vary the severity of the test by choosing other values of TIR than that specified in this method.

NOTE 2 It should be appreciated that a completely definitive result can only be reached by testing the whole batch, but in practice a balance is necessary between the statistical possibility of a definitive result and the cost of further testing.

NOTE 3 It is assumed that the following test parameters are set by the standard making reference to this standard:

- the type of striker and striker mass [see b) of clause 4 and item a) of 7.1];
- the drop height for the striker [see d) of clause 4 and 7.2, 7.3 and/or 7.4 as applicable];
- the method of sampling [see 5.1 and c) of clause 9];
- if appropriate, the number of test pieces to be used (see 5.2 and clause 7);
- the test and conditioning temperature and the conditioning medium (see clause 6);
- if applicable, any alternative or additional criterion for failure [see d) of 7.1].

4 Apparatus

A falling weight testing machine incorporating the following basic components (see Figure 1):

a) *main frame*, with guide rails or a guiding tube rigidly fixed in the vertical position to accommodate a striker [see b)] and release it to fall vertically and freely such that the speed of the striker at the moment of hitting the pipe is not less than 95 % of the theoretical speed;

b) *striker*, having a nose comprising all or part of a hemispherical form combined with a cylindrical stem at least 10 mm long and having dimensions conforming to Table 1 and Figure 2, depending upon the mass of the striker. The mass of the striker, including any associated weights, shall be selected from Table 2. Below the stem, the nose shall be of steel with a minimum wall thickness of 5 mm and the striking surface shall be free from imperfections which can influence the results.

c) *rigid test piece support*, consisting of a 120° vee-block at least 200 mm long, positioned so that the axis of the line of fall of the nose of the striker shall intersect the axes of the vee to within $\pm 2,5$ mm (see Figure 1).

The support construction shall be sufficiently rigid not to cushion the effect of the impact.

d) *release mechanism*, such that the falling weight can fall from a height which can be adjusted up to at least 2 m, as measured from the top surface of the test piece.

Table 1 — Dimensions for the nose of the striker

Type	R_s mm	d mm	d_s	a
d25	50	25	a	a
d90	50	90	a	a
a Not specified, to allow design freedom.				

Table 2 — Mass of strikers

Masses in kilograms

Mass of striker ± 0.005 kg			
Type d25	Type d90		
0,25	1,0	3,2	10,0
0,5	1,25	4,0	12,5
0,8	1,6	5,0	16,0
	2,0	6,3	
	2,5	8,0	



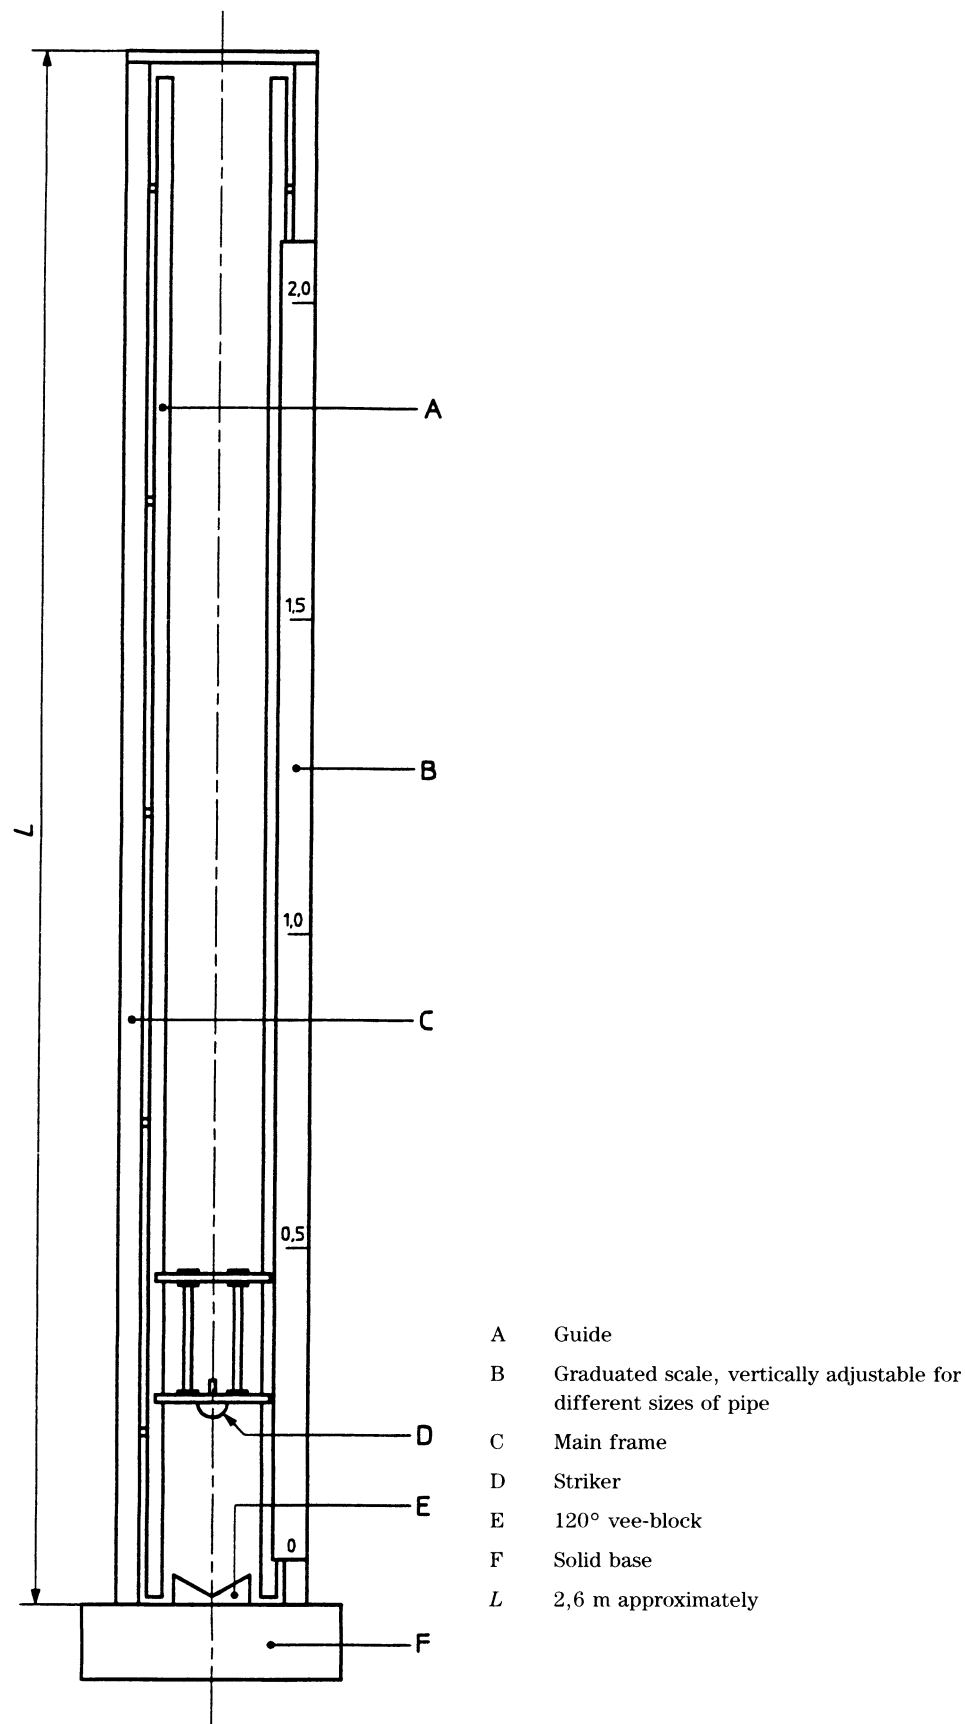


Figure 1 — Typical falling weight testing machine

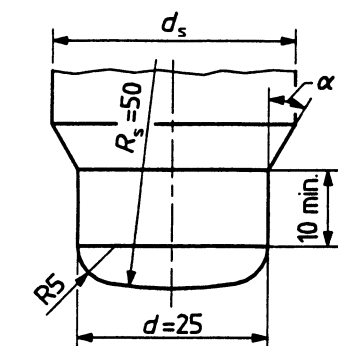

a) Type d25

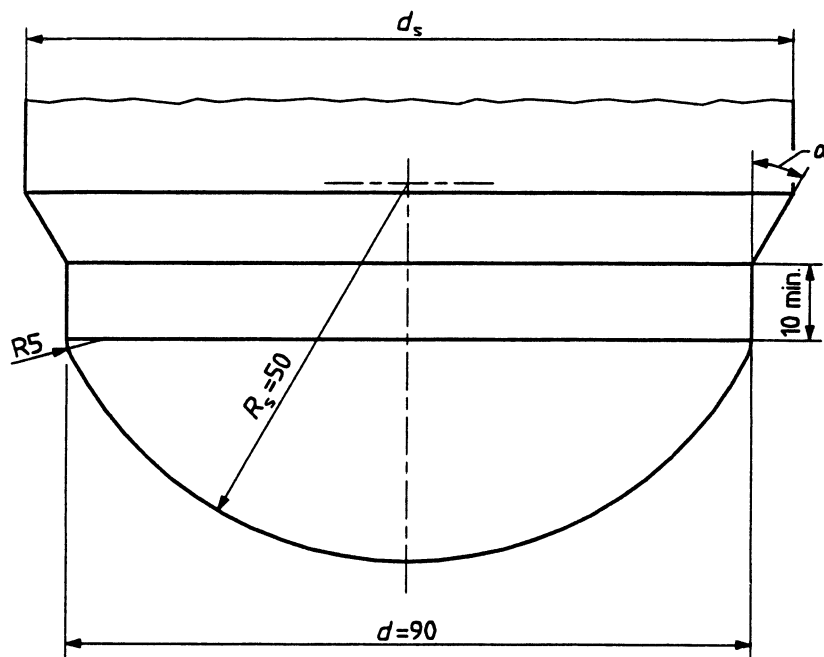

b) Type d90

Dimensions in millimetres

Figure 2 — Dimensions of strikers

5 Test pieces

5.1 Preparation

The test pieces shall be cut from pipes selected at random from a batch or from a product run from an extruder.

For each test piece, the length shall be (200 ± 10) mm.

The cut ends shall be square to the axis of the pipe, clean and free from damage.

For pipes with outside diameters greater than 40 mm, a number of longitudinal lines conforming to Table 3 shall be drawn with equidistant spacing around the pipe.

EXAMPLE. A straight line may be drawn along the length of the test piece at a random position. Further lines are drawn at successive equidistant intervals from one another (i.e. the last one is equidistant to the first one).

Table 3 — Number of equidistant lines to be drawn on the test pieces

Nominal outside diameter mm d_n^a	Number of equidistant lines to be drawn
$d_n \leq 40$	—
$40 < d_n \leq 63$	3
$63 < d_n \leq 90$	4
$90 < d_n \leq 125$	6
$125 < d_n \leq 180$	8
$180 < d_n \leq 250$	12
$250 < d_n \leq 355$	16
$355 < d_n$	24

^a For pipes with nominal diameters designated by other than d_n , their nominal size expressed in millimetres shall be taken in place of d_n .

5.2 Number

Taking into account that the number of test pieces necessary will depend upon:

- any applicable product sampling requirements (see 5.1);
- the size of the pipe under test;
- whether or not each test piece may be subject to more than one impact (see Table 3 and clause 7);
- the results obtained (see 7.5);

The number of test pieces shall be sufficient to enable at least one determination to be made in accordance with clause 8 (see Table 5 and the equations (1) and (2) as to whether the results obtained lie in region A, B or C.

The number of test pieces shall enable at least 25 blows to be applied.

6 Conditioning

The test pieces shall be conditioned in a bath of water and ice or air for not less than the applicable period given in Table 4. In the case of dispute over results, for 0 °C a bath of water and ice shall be used, and for – 20 °C air. For testing at 0 °C, the conditioning temperature shall be (0 ± 1) °C or for testing at – 20 °C, the conditioning temperature shall be (-20 ± 2) °C.

Table 4 — Conditioning periods

Wall thickness e mm	Conditioning period <i>min</i>	
	Bath of water and ice	Air
$e \leq 8,6$	15	60
$8,6 < e \leq 14,1$	30	120
$14,1 < e$	60	240

7 Procedure

7.1 Conduct the procedures given in 7.2 to 7.5 inclusive in accordance with the following conditions, as applicable:

- a) the striker [see b) of clause 4] shall have a mass selected from Table 2 in accordance with the referring standard;
- b) unless at least the environment for the test piece in the apparatus is maintained at the test temperature, each test piece shall be struck, one or more times as appropriate, within the following time interval after its removal from the conditioning environment:
 - 1) 10 s for $d_n \leq 110$ mm;
 - 2) 30 s for $110 < d_n \leq 200$ mm;
 - 3) 60 s for $d_n > 200$ mm.

If the applicable interval is exceeded, the test piece may still be used if it is returned to the conditioning environment within 10 s of the end of the interval and reconditioned for not less than 5 min. Otherwise the test piece shall be fully reconditioned or discarded;

c) for corrugated or ribbed pipe, if the pitch of the corrugation or ribs is more than 0,25 times the diameter d of the stem of the striker nose (see Figure 2), the test piece shall be positioned so that the initial impact of the striker will be on the top of a corrugation or a rib;

d) unless otherwise specified by the referring standard, consider as failure of the test piece shattering or any crack or split on the inside surface of the pipe that was caused by the impact and that can be seen without magnification: indentation of the test piece or a crease on the surface shall not be taken as a failure. Lighting devices may be used to assist in examining the test pieces. If criteria of failure other than those cited here are used, they shall be listed in the test report.

7.2 For pipes with a nominal outside diameter of 40 mm or less, subject each test piece to a single blow, using the appropriate mass of the falling striker and height of fall as specified in the referring standard, and record whether or not it failed [see d) of 7.1]. For all other pipe sizes, proceed in accordance with 7.3 unless the referring standard specifies testing by striking each test piece only once, in which case proceed in accordance with 7.4.

7.3 Subject a test piece to a blow by allowing the striker to fall from at least the specified height onto one of the marked lines (see 5.1 and note 3 to clause 3). If the test piece does not fail [see d) of 7.1] rotate it in the vee-block to the next marked line (see 5.1 and Table 3) and again subject it to a blow from the falling striker, after re-conditioning if necessary [see clause 6 and b) of 7.1].

Continue this procedure until the test piece fails or until all marked lines have received one blow, and record the numbers of blows and any failure accordingly.

7.4 If so required by the referring standard, carry out the test on successive test pieces by subjecting each test piece to a single blow and referring to d) of 7.1.

7.5 Taking into account the total numbers of blows struck and failures observed, determine whether a type A or type C result can be obtained in accordance with clause 8. If so, report the results in accordance with clause 9. If not, continue testing in accordance with 7.1 to 7.4 until a type A or type C result is determined or testing is abandoned with a consequent type B result.

8 Expression of results

The results shall be expressed as A, B or C for the batch, or the production run from an extruder, by reference to Table 5 or by calculation as follows.

Table 5 — Expression of TIR at 10 % depending on the number of blows and failures

Number of blows ^a	Number of failures		
	Region A Accept	Region B Continue test	Region C Reject
20 – 25	0	1 – 3	4
26 – 32	0	1 – 4	5
33 – 39	0	1 – 5	6
40 – 48	1	2 – 6	7
49 – 52	1	2 – 7	8
53 – 56	2	3 – 7	8
57 – 64	2	3 – 8	9
65 – 66	2	3 – 9	10
67 – 72	3	4 – 9	10
73 – 79	3	4 – 10	11
80	4	5 – 10	11
81 – 88	4	5 – 11	12
89 – 91	4	5 – 12	13
92 – 97	5	6 – 12	13
98 – 104	5	6 – 13	14
105	6	7 – 13	14
106 – 113	6	7 – 14	15
114 – 116	6	7 – 15	16
117 – 122	7	8 – 15	16
123 – 124	7	8 – 16	17

^a A minimum of 25 blows without failure shall be obtained before the test may be discontinued.

Boundaries between regions are calculated using the following equations:

$$S_{A/B} = np - 0,5 - u[np(1 - p)]^{0,5} \quad (1)$$

$$S_{B/C} = np + 0,5 + u[np(1 - p)]^{0,5} \quad (2)$$

where

u is 1,282 (10 % fractile one-sided);

p is 0,10 (TIR);

n is the number of blows.

NOTE 1 For convenience Figure 3 may be used as follows:

a) the result is “A” if the TIR is below 10 %, as indicated by the number of failures observed being in region A of Figure 3;

b) the result is “B” if no decision can be made on the basis of the number of test pieces used because the number of failures observed lies in region B of Figure 3 (however see A.2 of Annex A);

c) the result is “C” if the TIR is above 10 %, as indicated by the number of failures observed being in region C of Figure 3.

NOTE 2 The number of failed test pieces, as compared to the total number of blows, should not be expressed as a percentage, to avoid confusion with the TIR of which the percentage is only an estimate.

9 Test report

The test report shall include the following information:

- a) a reference to this standard and to the referring standard;
- b) the full identification of the pipe (e.g. application, material, dimensions);
- c) the description of the isolated batch or the continuous production run from which the test pieces were sampled and the method of sampling;
- d) the number of test pieces;
- e) the conditioning details including temperature in degrees Celsius, time and medium;
- f) the type of striker and its mass, in kilograms;
- g) the total number of failed test pieces;
- h) the total number of blows;
- i) the result as A, B or C (see clause 8), and if applicable details of any alternative or additional criterion for failure [see 7.1 d) and f) of note 3 to clause 3];
- j) any factors which may have affected the results, such as any incidents or any operating details not specified in this standard;

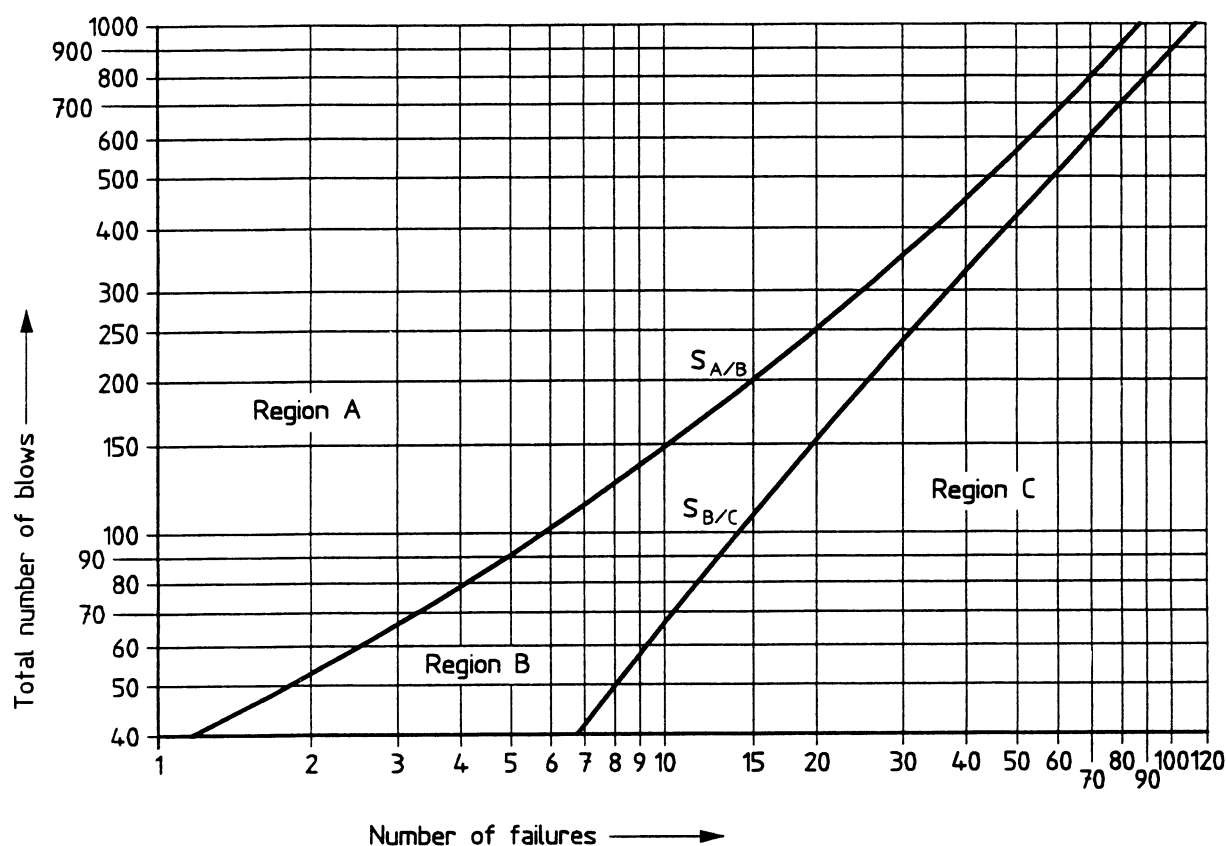


Figure 3 — Number of test pieces for 10 % TIR (at 90 % confidence level)

Annex A (informative)

Evaluation of results from isolated batches

A.1 General

This annex provides information on the evaluation of results from isolated batches of pipe and the use of Table 5, or, for values beyond those given in Table 5, equations (1) and (2), as applicable (see clause 8). This annex also recommends a procedure for sampling and testing from continuous production (see A.4).

The decision on the number of test pieces to be taken as a sample from an isolated batch should be made with the following consideration kept in mind.

Generally speaking, the precision of the test method is poor according to statistical laws. This is illustrated by the following examples:

- when testing to confirm a claim of 10 % TIR on a sample taken at random from a batch, if one test piece fails out of 100 blows, this indicates that the batch will have a TIR between 0,1 % and 3,9 % (with 90 % confidence);
- if five test pieces fail out of 100 blows, this indicates that the batch will have a TIR between 2,5 % and 9,1 % (with 90 % confidence);
- if nine test pieces fail out of 100 blows this indicates that the batch will have a TIR between 5,5 % and 13,8 % (with 90 % confidence).

A.2 Isolated batches with an independent quality mark (see the part on conformity assessment of the applicable system standard)

A.2.1 The procedure detailed in **A.2.2** makes use of the case where independent certification and monitoring is applied on the basis of the following assumptions:

- a) if from a sample the number of failures falls into region A (see clause 8) (for TIR less than or equal to 10 %), then reasonable confirmation is obtained that the batch has a TIR equal to or less than the specified level;
- b) if the number of failures falls into region C of Table 5, the batch can be judged to have a TIR greater than the specified value;
- c) if the number of failures falls into region B, generally further test pieces should be taken so that a decision can be reached. This decision is made by using the cumulative result of all the test pieces impacted from the batch under consideration.

A.2.2 If an isolated batch is claimed to have a TIR less than or equal to 10 % and this claim is supported by a quality mark, this can be confirmed as follows:

- a) if from a sample the number of failures falls into region A, then reasonable confirmation is obtained that the batch does have a TIR less than 10 %;
- b) if the number of failures falls into region B, the number of failures from the next sample has to fall in region A;
- c) if the number of failures falls into region C, the claim given by the quality mark is not confirmed.

EXAMPLE. Testing to confirm a claim of a TIR less than or equal to 10 %.

If the sample is large enough to allow use of 100 blows, the result is determined as follows:

- a) if after testing involving 100 blows there are up to or including 13 failures, reasonable confirmation is obtained that this batch has a TIR less than or equal to 10 %;
- b) if 14 or more failures occur, the claim given by the quality mark is not confirmed.

A.3 Isolated batches without a quality mark (see the part on conformity assessment of the applicable system standard)

If an isolated batch is claimed to have a TIR of less than or equal to 10 % but has no quality mark, this claim may be confirmed as follows:

- a) if from a sample the number of failures falls into region A, then reasonable confirmation is obtained that the batch has a TIR equal to or less than 10 %;
- b) if the number of failures falls into region C, the batch can be judged to have a TIR greater than 10 %;
- c) if the number of failures falls into region B, further test pieces should be taken so that a decision can be reached. This decision is made by considering the cumulative result of all the test pieces struck.

EXAMPLE. Testing to confirm a claim of a TIR less than or equal to 10 %.

If the sample is large enough to allow use of 100 blows, the result is determined as follows:

- a) if 5 or fewer failures occur the batch can be judged to have a TIR less than 10 %;
- b) if 14 or more failures occur, the batch can be judged to have a TIR greater than 10 %;

- c) if 6 to 13 failures occur, further blows are necessary for a decision to be reached (e.g. if after a further 50 blows there have been a total of 20 failures, the batch can be judged to have a TIR greater than 10 %).

A.4 A recommended sampling procedure: continuous production

The following sampling procedure is recommended for continuous production:

- a) at the commencement of a production run sufficient test pieces shall be impacted to demonstrate that the pipe has a TIR equal to or less than 10 % TIR in accordance with clause 8;
- b) thereafter, at intervals not exceeding 8 h, sufficient test pieces shall be taken to ensure that at least 20 impact blows may be made;
- c) if no failures occur in the sample taken in accordance with A.4, production may proceed;
- d) in the event of a failure occurring, in the sample taken in accordance with A.4, further test pieces shall be tested until a pass or fail decision is reached in accordance with clause 8 (i.e. the number of failures shall be in region A or C respectively).

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.